

c -axis phase coherence and spin fluctuations in cuprates

A. Mourachkine

Université Libre de Bruxelles, CP-232, Blvd du Triomphe, B-1050 Brussels, Belgium

(Received 5 June 2000)

Abstract. - There is a consensus that superconductivity (SC) in cuprates is two-dimensional. It is widely believed that the long-range phase coherence appears at T_c due to the Josephson coupling between SC CuO_2 (bi-, tri-, ...) layers. Recent T_c and resistivity measurements in $\text{Ti}_2\text{Ba}_2\text{CaCu}_2\text{O}_8$ as a function of applied pressure (Salvetat J.-P. *et al.*, *Europhys. Lett.*, **52** (2000) 584) show that the interlayer Josephson-coupling mechanism does not fit the data. Here we analyze data obtained in Andreev reflection, neutron scattering, microwave, muon spin relaxation, tunneling and resistivity measurements performed on different cuprates, mainly, on $\text{YBa}_2\text{Cu}_3\text{O}_{6+x}$, $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+x}$ and $\text{La}_{2-x}\text{Sr}_x\text{CuO}_{4+y}$. The analysis of the data shows that the long-range phase coherence in the cuprates intimately relates to antiferromagnetic interactions along the c axis. At the same time, it seems that the in-plane mechanism of the SC has no or little relations to the magnetic interactions along the c axis.

74.25.-q; 74.72.-h; 74.25.Ha

I. INTRODUCTION

Superconductivity (SC) and magnetism were earlier considered as mutually exclusive phenomena. Recent research revealed a rich variety of extraordinary SC and magnetic states and phenomena in novel materials that are due to the interaction between SC and magnetism [1]. The coexistence of SC and long-range antiferromagnetic (AF) order was first discovered in RMO_6Se_8 ($R = \text{Gd}, \text{Tb}$ and Er), RRh_4B_4 ($R = \text{Nd}, \text{Sm}$ and Tm), and RMO_6S_8 ($R = \text{Gd}, \text{Tb}, \text{Dy}$ and Er) [1]. Later, coexistence of SC and AF order was found in U-based heavy fermions (UPt_3 , URu_2Si_2 , UNi_2Al_3 , UPd_2Al_3 , U_6Co , and U_6Fe), in heavy fermions RRh_2Si_2 ($R = \text{La}$ and Y), $\text{Cr}_{1-x}\text{Re}_x$, CeRu_2 , in borocarbides $\text{RNi}_2\text{B}_2\text{C}$ ($R = \text{Tm}, \text{Er}, \text{Ho}, \text{Dy}$), in organic SCs [1,2] and in the new heavy fermion $\text{CeRh}_{1-x}\text{Ir}_x\text{In}_5$ [3]. In $\text{CeRh}_{0.5}\text{Ir}_{0.5}\text{In}_5$, the bulk SC coexists *microscopically* with small-moment magnetism ($\leq 0.1\mu_B$) [3]. In all other heavy fermions, there are strong AF correlations present in the SC state [1,2,3]. Another class of materials in which SC and AF coexist are copper oxides (cuprates) such as $\text{YBa}_2\text{Cu}_3\text{O}_{6+x}$ (YBCO) and $\text{La}_{2-x}\text{Sr}_x\text{CuO}_{4+y}$ (LSCO) compounds [1]. Coexistence of SC and ferromagnetic (FM) order is found in the heavy fermion UGe_2 [4], and in Ru-based materials, for example, in $\text{RuSr}_2\text{GdCu}_2\text{O}_8$ [5].

In SC heavy-fermion systems, spin fluctuation (electron-electron interactions) are believed to mediate the electron pairing that leads to SC [6]. For the heavy fermions CeIn_3 , CePd_2Si_2 [7], UPd_2Al_3 [8] and UGe_2 [4], there is an indirect evidence for spin-fluctuation mechanism of SC. This intimate relationship between the SC and magnetism also appears to be central to cuprates [1] which inherited magnetic properties from their parent compounds, AF Mott insulators. Many theoretical studies suggest that the SC in cuprates is mediated via the exchange of AF spin fluctuations [9].

There is a consensus that, in the underdoped regime

of cuprates, there are two energy scales [10]: the pairing energy scale, Δ_p , and the phase-coherence scale, Δ_c , observed experimentally [10,11]. The two energy scales have different dependences on hole concentration, p , in CuO_2 planes (see fig. 3): Δ_p increases linearly with decrease of hole concentration, whereas Δ_c has approximately the parabolic dependence on p and scales with T_c as $2\Delta_c \simeq 5.4k_B T_c$ [10].

There is a consensus that the SC in cuprates is two-dimensional (2D). It is widely believed that the long-range phase coherence occurs at T_c due to the Josephson coupling between SC CuO_2 (bi-, tri-, ...) layers. Recent measurements of the in-plane (ρ_{ab}) and out-of-plane (ρ_c) resistivities in $\text{Ti}_2\text{Ba}_2\text{CaCu}_2\text{O}_8$ as a function of applied pressure show that $\rho_c(T)$ shifts smoothly down with increase of pressure, however, T_c first increases and then *decreases* [12]. This result can not be explained by the interlayer Josephson-coupling mechanism. The authors conclude [12]: "Any model that associates high- T_c with the interplane Josephson coupling should therefore be revisited." In this paper, we analyze data obtained in Andreev reflection, inelastic neutron scattering (INS), microwave, muon spin relaxation (μSR), tunneling and resistivity measurements performed on different cuprates, mainly, on YBCO, $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+x}$ (Bi2212) and LSCO. The analysis of the data shows that the long-range phase coherence in the cuprates intimately relates to AF interactions along the c axis [13]. At the same time, it seems that the in-plane mechanism of the SC has no or little relations to the magnetic interactions along the c axis. We also analyze data measured in heavy fermions UPt_3 , UPd_2Al_3 and CeIrIn_5 , and in some layered non-SC compounds with FM correlations.

II. IN-PLANE AND C -AXIS TUNNELING IN Bi2212

Tunneling spectroscopy is a unique probe of SC state in that it can, in principle, reveal the quasiparticle density of states directly with high energy resolution. Figure 1 shows the temperature dependence of in-plane tunneling quasiparticle peaks, measured in slightly overdoped Bi2212 single crystals [14,15,16,17]. Tunneling measurements performed on slightly underdoped Bi2212 single crystals show similar temperature dependence [18]. So, the temperature dependence of in-plane quasiparticle peaks shown in fig. 1 can be considered as a typical one. In fig. 1, we present also the temperature dependence of c -axis quasiparticle peaks measured in slightly overdoped Bi2212 mesas [19]. Measurements performed on micron-size mesas present *intrinsic* properties of the material. In fig. 1, surprisingly, the temperature dependences along the ab planes and along the c axis are *different*. It is a clear hallmark of coexistence of two different SC mechanisms in Bi2212: in-plane and along the c axis.

III. LSCO

In LSCO, there is an evidence that the SC intimately relates to the establishment of AF order along the c axis.

Recent μ SR measurements performed on non-SC Eu-doped LSCO having different hole concentrations show that the SC phase of pure LSCO is replaced in Eu-doped LSCO by the second AF phase (see fig. 4 in Ref. [20]). Thus, the data show that it is possible to switch the entire hole concentration dependent phase diagram from SC to AF. It is a clear hallmark that the SC in LSCO intimately relates to the formation of AF order. We return to this important result later.

We turn now to the analysis of resistivity data measured in non-SC 2D layered compounds with AF or FM correlations. The data clearly show that, in all these layered compounds, the out-of-plane resistivity, ρ_c , has drastic changes either at Néel temperature, T_N , or Curie temperature, T_C , whereas the in-plane resistivity, ρ_{ab} , passes through T_N or T_C smoothly.

We start with YBCO. In AF undoped YBCO ($x = 0.35$; 0.33 ; and 0.32) having $T_N \simeq 80$ K, 160 K, and 210 K, respectively, ρ_c shows sharp increase, by about 2 orders of magnitude, upon cooling through T_N [21]. At the same time, ρ_{ab} changes at T_N smoothly. The same effect has been observed in LuBCO ($x = 0.34$) [22]. So, the Néel ordering in undoped YBCO has remarkably different impact on the electron transport within CuO_2 planes and between them. The authors conclude [21]: “The Néel temperature actually corresponds to the establishment of AF order along c axis.”

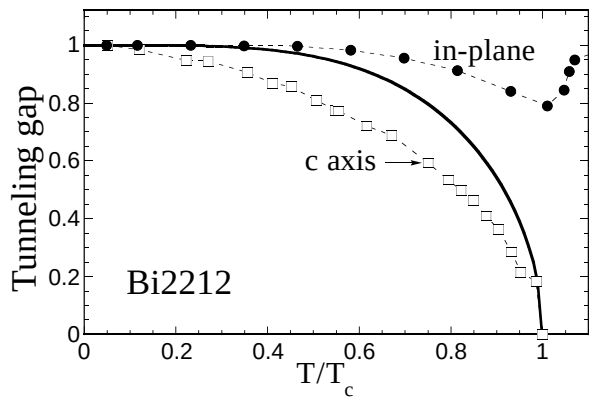



FIG. 1. Temperature dependences of in-plane (dots) [14-17] and c -axis tunneling quasiparticle peaks (squares) [19] in slightly overdoped Bi2212 single crystals, $\Delta(T)/\Delta(T_{min})$. The BCS temperature dependence is shown by the solid line. The dashed lines are guides to the eye.

We now discuss FM layered compounds. The structure of the FM compound $\text{Bi}_2\text{Sr}_3\text{Co}_2\text{O}_9$ (BSCoO) is similar to the structure of Bi2212, where CoO_2 planes are analogous with CuO_2 planes in Bi2212 [23]. BSCoO becomes FM at $T_C = 3.2$ K. The resistivity data show that, at T_C , there is a cusp in ρ_c but ρ_{ab} changes smoothly. The authors conclude that the long-range magnetic order in BSCoO develops at T_C along the c axis [23]. In layered manganite $\text{La}_{1.4}\text{Sr}_{1.6}\text{Mn}_2\text{O}_7$ (LSMO) which is composed of the MnO_2 bilayers becomes FM at $T_C = 90$ K [24]. The resistivity data show that, at T_C , there are drastic changes in ρ_c (a few orders of magnitude), but very small changes in ρ_{ab} . They conclude that, in LSMO, the long-range magnetic order develops at $T_C = 90$ K along the c axis [24].

Neutron-scattering measurements performed on the heavy fermion URu_2Si_2 ($T_c = 1.2$ K) show that the AF order develops at $T_N = 17.5$ K along the c axis [25]. So, it seems that, in all layered compounds, the long-range AF or FM order develops at T_N or T_C along the c axis (the *in-plane* magnetic correlations exist above T_N and T_C [24]).

We now return to the analysis of the phase diagram of non-SC Eu-doped LSCO, where the SC phase of pure LSCO is replaced by the second AF phase [20]. The conclusion made in the previous paragraph signifies that either the main AF phase of Eu-doped LSCO or the second AF phase develops along the c axis. Thus, the SC phase of pure LSCO is replaced in Eu-doped LSCO by the AF phase which develops along the c axis. Consequently, the SC in LSCO intimately relates to the establishment of the long-range AF order along the c axis.

In heavy fermion CeIrIn_5 , μ SR measurements discovered the onset of a small magnetic field (~ 0.4 Gauss) which sets exactly at T_c [3]. In YBCO ($x = 0.6$), recent INS measurements identified small magnetic moments directed along the c axis, which increase in strength at and

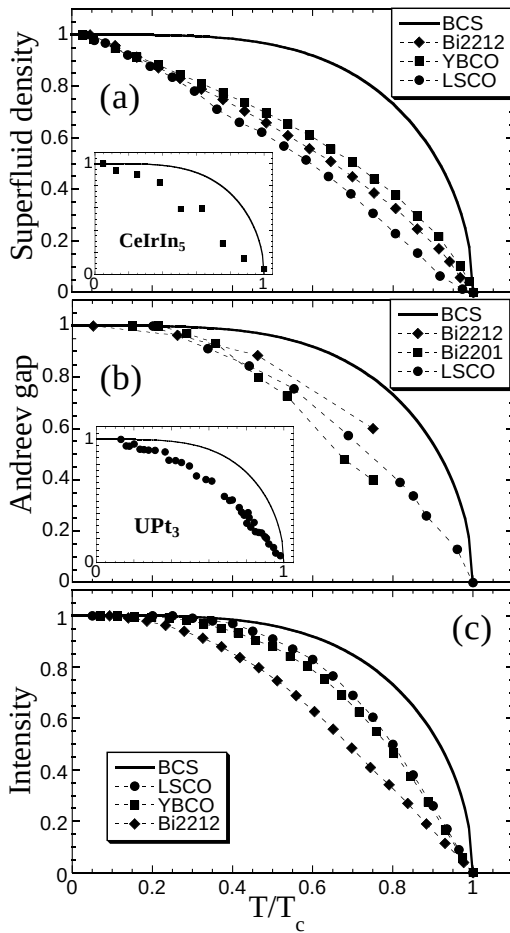

below T_c [26].

IV. YBCO, BI2212 AND LSCO

We now compare coherence SC and magnetic characteristics of YBCO, Bi2212 and LSCO. The comparison shows that the magnetic and coherence SC characteristics have similar temperature dependencies, and, at different dopings, their magnitudes are proportional to each other (and proportional to T_c). Thus, the coherence SC and magnetic properties of cuprates intimately relate to each other.

First, we describe the magnetic properties of cuprates. The low energy magnetic excitations in LSCO cuprate have been extensively studied, and the observed spin fluctuations are characterized by wave vector which is incommensurate with the lattice [27]. These modulated spin fluctuations in LSCO persist in both normal and SC states. The spin dynamics in YBCO and Bi2212 studied by INS exhibit below T_c a sharp commensurate resonance peak which appears at well defined energy E_r [28,29,30,31,32,33,34,35,36,37,38]. Incommensurability in YBCO has been also reported [35], and it is

FIG. 2. (a) Temperature dependence of the superfluid density in near optimally doped single crystals of Bi2212 ($T_c = 93$ K) [40] and YBCO ($T_c = 93$ K) [41], and in an overdoped LSCO ($x = 0.2$) single crystal ($T_c = 36$ K) [42]. The superfluid density is proportional to $1/\lambda^2(T)$, where $\lambda(T)$ is the magnetic penetration depth. Inset: temperature dependence of the superfluid density in heavy fermion CeIrIn₅ ($T_c = 0.4$ K) [3] (axis parameters as main plot). (b) Temperature dependence of Andreev-reflection gap, $\Delta(T)/\Delta(T_{min})$, in an overdoped Bi2212 thin film ($T_c = 80$ K) [43], and in overdoped single crystals of Bi2201 ($T_c = 29$ K) [44] and LSCO ($x = 0.2$) ($T_c = 28$ K) [45]. Inset: temperature dependence of the Andreev gap in heavy fermion UPt₃ ($T_c \sim 440$ mK) [48] (axis parameters as main plot). (c) Temperature dependence of the peak intensity of the incommensurate elastic scattering in LSCO ($x = 0$) ($T_c = 42$ K) [27] and the intensity of the magnetic resonance peak measured by INS in near optimally doped Bi2212 ($T_c = 91$ K) [28] and YBCO ($T_c = 92.5$ K) [33]. The neutron-scattering data are average, the real data have the vertical error of the order of $\pm 10\%$ [27,28,33]. The BCS temperature dependence is shown by the thick solid line. The dashed lines are guides to the eye.

consistent with that in LSCO of the same hole doping, but, in YBCO, it occurs in the SC state. Now it is clear that the incommensurability and the commensurate resonance are inseparable parts of the general features of the spin dynamics in YBCO at all doping levels [39]. Thus, there is a clear evidence of coexistence of AF order and SC below T_c , at least, in LSCO and YBCO.

We now compare coherence SC and magnetic characteristics of the cuprates. Figure 2(a) shows the temperature dependences of the superfluid density in near optimally doped single crystals of Bi2212 [40] and YBCO [41], and in an overdoped LSCO ($x = 0.2$) single crystal [42], measured by microwave, μ SR and ac-susceptibility techniques, respectively. The superfluid density is proportional to $1/\lambda^2(T)$, where $\lambda(T)$ is the magnetic penetration depth. Figure 2(b) shows the temperature dependences of Andreev-reflection gap measured in an overdoped Bi2212 thin film [43], and in overdoped single crystals of Bi2201 [44] and LSCO ($x = 0.2$) [45]. It is important to emphasize that Andreev reflections are exclusively sensitive to coherence properties of the condensate. In figs 2(a) and 2(b), one can see that there is a good agreement among temperature dependences of coherence SC characteristics of different cuprates.

Figure 2(c) shows the temperature dependences of the peak intensity of the incommensurate elastic scattering in LSCO ($x = 0$) [27] and the intensity of the commensurate resonance peak measured by INS in near optimally doped Bi2212 [28] and YBCO [33].

In fig. 2, all temperature dependences of coherence SC and magnetic characteristics exhibit below T_c a striking similarity. Since all temperature dependences shown in fig. 2 are similar to the temperature dependence of c -axis quasiparticle peaks in Bi2212, shown in fig. 1, and

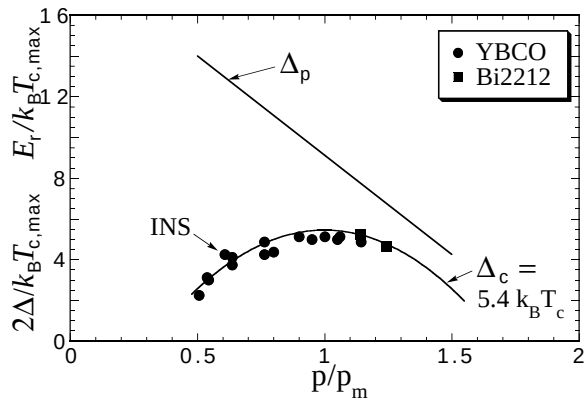


FIG. 3. The phase diagram of cuprates (lines) [10] and the energy position of the magnetic resonance peak, E_r , in Bi2212 [28,29] and in YBCO [30–38] at different hole concentrations ($p_m = 0.16$). When not available, p has been calculated from the relation $T_c/T_{c,max} = 1 - 82.6(p - 0.16)^2$ [50], and we use $T_{c,max} = 93$ K and $T_{c,max} = 95$ K in the case of YBCO and Bi2212, respectively.

different from the temperature dependence of in-plane quasiparticle peaks, shown also in fig. 1, it is reasonable to assume that the coherence SC and magnetic properties of the cuprates intimately relate to each other along the c axis. Moreover, in YBCO ($x = 0.6$), recent INS measurements found small magnetic moments directed along the c axis, which increase in strength at and below T_c [26]. At the same time, as one can see in figs 1 and 2, the in-plane mechanism of the SC in the cuprates has no or little relations to the magnetic interactions along the c axis.

Figure 3 shows the phase diagram of cuprates [10]. As noted earlier, Δ_p is the pairing energy scale, and Δ_c is the energy scale which is responsible for the long-range phase coherence and proportional to T_c as $2\Delta_c \simeq 5.4k_B T_c$ [10]. At different doping levels, Andreev-reflection data coincide with Δ_c [10,11,45]. In fig.3, we present also the energy position of the magnetic resonance peak, E_r , in Bi2212 [28,29] and in YBCO [30,31,32,33,34,35,36,37,38] as a function of doping. In fig.3, one can see that, at different dopings, E_r is proportional to Δ_c as $E_r \simeq 2\Delta_c$. This correlation suggests that spin excitations are responsible for establishing the phase coherence in YBCO and Bi2212 since the relation $E_r \simeq 2\Delta_c$ is in a good agreement with the theories in which SC is mediated by spin fluctuations [9]. Recently, it was shown that applied magnetic fields suppress the magnetic resonance peak in YBCO indicating that the resonance peak, indeed, measures the long-range phase coherence [46]. The strength of coupling between spin excitations and charge carriers is sufficient to account for the high T_c value in cuprates [47].

What is interesting is that all temperature dependences shown in fig.2 are similar to the temperature

dependence of the superfluid density in heavy fermion CeIrIn₅, measured by μ SR [3], and to the temperature dependence of the Andreev-reflection gap in heavy fermion UPt₃ [48], which are shown in the insets of figs 2(a) and 2(b), respectively. Spin fluctuations are believed to mediate the electron pairing in CeIrIn₅ [3] and UPt₃ [6] that leads to SC. The magnetic resonance peak has not yet been detected in CeIrIn₅ or UPt₃, however, the magnetic resonance peak has been observed by INS in another heavy fermion UPd₂Al₃ [49] where spin fluctuations mediate the SC which coexists with the long-range AF order [8]. The latter facts point also to presence of spin-fluctuation coupling mechanism in cuprates.

The behavior of all temperature dependences shown in fig. 2 can be easily understood in terms of the spin-fluctuation mechanism of SC (electron-electron interactions): crudely speaking, they exhibit the squared BCS temperature dependence.

V. DISCUSSION

In spite of the unmistakable similarities among the magnetic and SC properties of YBCO, Bi2212 and LSCO (and some heavy fermions for which there is an indirect evidence for spin-fluctuation mechanism of SC), clearly, there is a difference between magnetic properties of LSCO and YBCO. If, in YBCO, $T_c \simeq T_{com} \simeq T_{inc}$, where T_{com} (T_{inc}) is the onset temperature of the (in-) commensurate peak(s), in LSCO, the situation is different. First, the commensurate peak has not been detected. Second, in LSCO, mainly, $T_c < T_{inc}$ (Figure 2(c) shows the case when $T_c = T_{inc}$). So, the magnetic and SC properties of LSCO are similar to those of most heavy fermions: the commensurate peak has not been detected, and $T_c < T_N$. For example, in UPd₂Al₃, $T_c \approx 2$ K and $T_N = 14.5$ K [8,49]; in URu₂Si₂, $T_c \approx 1.2$ K and $T_N = 17.5$ K [25], and, in FM heavy fermion UGe₂, $T_c < T_C$ [4]. In Bi2212, the situation looks more like that of YBCO, even if, the incommensurate peaks have not *yet* been detected. Apparently, it is only a question of time.

In fact, the differences between magnetic and SC properties of YBCO and LSCO (and among some heavy fermions) can be understood in terms of the chain of the following events: the formation of pairs at T_{pair} - the SC order parameter couples to the magnetic in-plane order parameter - the appearance of AF interactions along the c axis at T_m - the appearance of the long-range SC phase coherence. If there is no pairs, the SC is absent, even if, the AF order is established (like in the Eu-doped LSCO [20]). If $T_{pair} < T_m$, then, it reminds the situation in LSCO where $T_c < T_{inc}$. If $T_{pair} > T_m$, then, it reminds the case of YBCO where $T_c = T_{com} = T_{inc}$, and, consequently, $T_c = T_m$. Unfortunately, this naive picture cannot explain the presence of the commensurate peak in INS spectra but, at least, shows that the differences

between the magnetic and SC properties of LSCO and YBCO can be understood in frameworks of one picture with different initial parameters.

VI. SUMMARY

The analysis of the data obtained by different techniques in YBCO, Bi2212 and LSCO shows that the long-range phase coherence intimately relates to AF interactions along the c axis. At the same time, it seems that the in-plane mechanism of the SC has no or little relations to the magnetic interactions, at least, along the c axis. Apparently, in cuprates, the magnetic and SC order parameters are coupled to each other, and the phase-coherence scale, Δ_c , has the magnetic origin (see fig. 3).

There are common features in the SC state of the heavy fermions CeIrIn₅, UPt₃ and UPd₂Al₃, on the one hand, and the cuprates, on the other hand. It is possible that, in all heavy-fermion and organic SCs, the long-range phase coherence is also established due to spin fluctuations (the pairing mechanism may be different).

-
- [1] Maple M. B., *Physica C*, **341-348** (2000) 47, and *Physica B*, **215** (1995) 110.
 - [2] Gabovich A. M. and Voitenko A. I., *Fiz. Nizk. Temperatur*, **26** (2000) 419.
 - [3] Heffner R. H. *et al.*, cond-mat/0102137; Pagliuso P. G. *et al.*, cond-mat/0101316; and Petrovic C. *et al.*, cond-mat/0012261.
 - [4] Saxena S. S. *et al.*, *Nature*, **406** (2000) 587.
 - [5] Bernhard C. *et al.*, *Phys. Rev. B*, **59** (1999) 14099.
 - [6] Miyake K., Schmitt-Rink S., and Varma C. M., *Phys. Rev. B*, **34** (1986) 6554.
 - [7] Martur N. D. *et al.*, *Nature*, **394** (1998) 39.
 - [8] Hunt M. and Jordan M., in *Advances in Solid State Physics*, Vol. 39, edited by Kramer B. (Vieweg, Braunschweig/Wiesbaden) 1999, p. 351, and Jordan M., Hunt M., and Adrian H., *Nature*, **398** (1999) 47.
 - [9] See, for example, Morr D. K. and Pines D., *Phys. Rev. Lett.*, **81** (1998) 1086.
 - [10] Deutscher G., *Nature*, **397** (1999) 410.
 - [11] Mourachkine A., *Europhys. Lett.*, **50** (2000) 663.
 - [12] Salvétat J.-P., Berger H., Halbritter A., Mihaly G., Pavuna D., and Forro L., *Europhys. Lett.*, **52** (2000) 584.
 - [13] However, the intra-bilayer (trilayer *etc.*) coupling may arise from the Josephson coupling.
 - [14] Ekino T. *et al.*, *Phys. Rev. B*, **60** (1999) 6916.
 - [15] Matsuda A., Sugita S., and Watanabe T., *Phys. Rev. B*, **60** (1999) 1377.
 - [16] Mourachkine A., *Europhys. Lett.*, **49** (2000) 86.
 - [17] Oda M. *et al.*, oral presentation at the New³SC-3 Conference in Honolulu (Hawaii USA), 15-19 January 2001 (to be published in *Physica C*).
 - [18] Miyakawa N. *et al.*, *Phys. Rev. Lett.*, **83** (1999) 1018.
 - [19] Krasnov V. M. *et al.*, *Phys. Rev. Lett.*, **84** (2000) 5860.
 - [20] Klaus H.-H. *et al.*, *Phys. Rev. Lett.*, **85** (2000) 5490.
 - [21] Lavrov A. N. *et al.*, *Phys. Rev. Lett.*, **83** (1999) 1419.
 - [22] Lavrov A. N., Ando Y., and Segawa K., *Physica C*, **341-348** (2000) 1555.
 - [23] Tsukada I. *et al.*, cond-mat/0012395.
 - [24] Kimura T. *et al.*, *Science*, **274** (1996) 1698.
 - [25] Broholm C. *et al.*, *Phys. Rev. Lett.*, **58** (1987) 1467.
 - [26] Mook H. A., Dai P., and Dogan F., cond-mat/0102047.
 - [27] Lee Y. S. *et al.*, *Phys. Rev. B*, **60** (1999) 3643.
 - [28] Fong H. P. *et al.*, *Nature*, **398** (1999) 588.
 - [29] He H. *et al.*, *Phys. Rev. Lett.*, **86** (2001) 1610.
 - [30] Bourges Ph., in *The Gap Symmetry and Fluctuations in High Temperature Superconductors*, edited by Bok J., Deutscher G., Pavuna D., and Wolf S. A. (Plenum Press) 1998, p. 349.
 - [31] Fong H. F. *et al.*, *Phys. Rev. B*, **61** (2000) 14773.
 - [32] Regnault L. P. *et al.*, *Physica C*, **235-240** (1994) 59.
 - [33] Dai P. *et al.*, *Science*, **284** (1999) 1344.
 - [34] Bourges Ph. *et al.*, *Europhys. Lett.*, **38** (1997) 313.
 - [35] Dai P., Mook H. A., and Dogan F., *Phys. Rev. Lett.*, **80** (1998) 1738.
 - [36] Fong H. F. *et al.*, *Phys. Rev. Lett.*, **78** (1997) 713.
 - [37] Mook H. A. *et al.*, *Phys. Rev. Lett.*, **70** (1993) 3490.
 - [38] Fong H. F. *et al.*, *Phys. Rev. Lett.*, **75** (1995) 316.
 - [39] Dai P. *et al.*, *Phys. Rev. B*, **63** (2001) 054525.
 - [40] Lee S.-F. *et al.*, *Phys. Rev. Lett.*, **77** (1995) 735.
 - [41] Sonier J. E. *et al.*, *Phys. Rev. Lett.*, **83** (1999) 4156.
 - [42] Panagopoulos C. *et al.*, cond-mat/9911116.
 - [43] Plecenik A. *et al.*, in *Studies of High Temperature Superconductors*, Vol. 20, edited by Narlikar A. V. (Nova Science, New York) 1996, p. 75.
 - [44] Li S.-X. *et al.*, *Physica C*, **338** (2000) 213.
 - [45] Gonnelli R. S. *et al.*, cond-mat/0101209.
 - [46] Dai P. *et al.*, *Nature*, **406** (2000) 965.
 - [47] Carbotte J. P., Schachinger E., and Basov D. N., *Nature*, **401** (1999) 354.
 - [48] De Wilde Y. *et al.*, *Phys. Rev. Lett.*, **72** (1994) 2278.
 - [49] Metoki N. *et al.*, *Phys. Rev. Lett.*, **80** (1998) 5417.
 - [50] Presland M. R. *et al.*, *Physica C*, **165** (1991) 391.